



Carondelet Division

8600 Commercial Blvd. • Pevely, MO 63070 USA

Phone: 636-475-2199 • Fax: 636-479-3399

E-Mail: Charles.Ruud@MetalTek.com

Corrective Action 1671
Carondelet Division
Corrective Action Type NCR
Date 4-10-06 Revised **5-5-06**
CA Originator C. Ruud
Applies to: A-6 Coil

Description of Defect / Non-Conformance

Test bar from zone 1 failed elongation at -320 F. Result was 20% versus a minimum of 32%. The original set of three bars, Z-1, Z-2 and Z-3 were sent for testing. Z-1 failed for elongation, 26% vs 32% minimum and Z-3 failed for elongation 19% vs 32% minimum. All other results were acceptable. Retests were ordered. The second results were similar. Z-1 failed for elongation, 25% vs 32% minimum and Z-3 failed for elongation 13% vs 32% minimum, but broke outside the gauge length. The third set of bars was tested. Z-3 passed and Z-1 failed for elongation, 20% vs 32% minimum, but broke outside the gauge length. All other test results were acceptable. See attached test reports. A fourth set of 3 test bars were tested. All results were acceptable. See last report. Please note that the identification of these bars was not readable, but it is believed that they came from zones 1, 2 and 3. **Failed test bars indicated flaws attributed to the failure.**

Root Cause

See attached report, with attachments.

Corrective Action

Use A-6 as is.


Actual Completion Date

Completed 4/20/06.

Signed: C. Ruud

A handwritten signature in black ink, appearing to read "C. Ruud", written over a horizontal line.

CC: B. Craig, J. Edwards, E.J. Kubick, J. Markham, J. Galaske

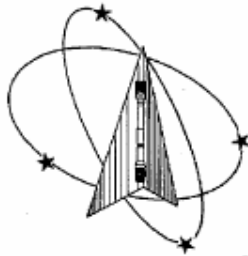

Westmoreland Mechanical Testing & Research, Inc.

P.O. Box 388
 Westmoreland Drive
 Youngstown, Pa. 15696-0388 U.S.A.
 Telephone: 724-537-3131 Fax: 724-537-3151

Website: www.wmtr.com

WMTR is a technical leader in the material testing industry.



621-01 & 621-02



March 9, 2006

MetalTek International
 The Carondelet Division
 8600 Commercial Blvd.
 I-55 Industrial Park
 Pevsly, MO 63070-1528

Attention: Jim Galaske

Subject: All processes, performed upon the material as received, were conducted at WMT&R, Inc. in accordance with the WMT&R Quality Assurance Manual, Rev. 9, dated 4/1/2000.

The following tests were performed on this order: TENSILE

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max ---) 0.2% YS ksi (Min 72Max ---) 4D Elong. % (Min 32Max ---) Modulus Msi (Min 21Max ---)

SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: 316 S/S

| Coil No. | Specimen Number | TestLog Temp. °F | UTS ksi | 0.2% YS ksi | Elong % | RA % | Modulus Msi | Ult. Load lbf | 0.2% YLD. lbf | Orig. Dia. (in.) | Final Dia. (in.) | 4D Orig. GL (in.) | 4D Final GL (in.) | Orig. Area (sq. in.) | Machine Number | AIUR |
|----------|-----------------|------------------|---------|-------------|---------|------|-------------|---------------|---------------|------------------|------------------|-------------------|-------------------|----------------------|----------------|------|
| A6 | Z2 | D18313 | 163.7 | 100.1 | 61 | 41 | 28.0 | 15730 | 9616 | 0.3498 | 0.2898 | 1.40 | 2.25 | 0.09610135 | M9 | A |

DISPOSITION: Acceptable

AIUR: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max ---) 0.2% YS ksi (Min 72Max ---) 4D Elong. % (Min 32Max ---) Modulus Msi (Min 21Max ---)

SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: 316 S/S

| Coil No. | Specimen Number | TestLog Temp. °F | UTS ksi | 0.2% YS ksi | Elong % | RA % | Modulus Msi | Ult. Load lbf | 0.2% YLD. lbf | Orig. Dia. (in.) | Final Dia. (in.) | 4D Orig. GL (in.) | 4D Final GL (in.) | Orig. Area (sq. in.) | Machine Number | AIUR |
|----------|-----------------|------------------|---------|-------------|---------|------|-------------|---------------|---------------|------------------|------------------|-------------------|-------------------|----------------------|----------------|------|
| A6 | Z1 | D18312 | 161.1 | 108.9 | 26 | 30 | 29.7 | 15470 | 10460 | 0.3497 | 0.2929 | 1.40 | 1.76 | 0.09604641 | M9 | U |
| A6 | Z3 | D18314 | 157.5 | 111.2 | 19 | 28 | 30.9 | 15140 | 10690 | 0.3498 | 0.2959 | 1.40 | 1.67 | 0.09610135 | M9 | U |


DISPOSITION: Unacceptable

AIUR: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

Matthew Wojcik
 Roy E. Stein/Matt Wojcik
 Technical Services Manager
 3-9-06
 March 9, 2006

WARNING: DO NOT FULLY QUALIFY OR CONSIDER A MATERIAL FACT ON THIS FORM OR HAVING PUBLIC NOTICES OR FAVORABLE REPRESENTATIONS OR REPRESENTATIONS HEREIN. THIS CERTIFICATE OR REPORT SHALL NOT BE REPRODUCED EXCEPT IN FULL WITHOUT THE WRITTEN APPROVAL OF WMTR, INC.

Testing Specialists for Aerospace, Automotive, and Material Testing Fields
 Locations in Youngstown, PA U.S.A. - Tel (724) 537-3131 and



Westmoreland Mechanical Testing & Research, Inc.
 P.O. Box 388
 Westmoreland Drive
 Youngstown, Pa. 15696-0388 U.S.A.
 Telephone: 724-537-3131 Fax: 724-537-3151
 Website: www.wmtr.com



WMT&R is a technical leader in the material testing industry.

April 3, 2006

MetalTek International
 The Carondelet Division
 8600 Commercial Blvd.
 I-55 Industrial Park
 Pevely, MO 63070-1528

CERTIFICATION

Section 1 of 1
 WMT&R Report No. 6-25662
 P.O. No. 19386
 Requisition No. 7580

Attention: Jim Galasko

Subject: All processes, performed upon the material as received, were conducted at WMT&R, Inc. in accordance with the WMT&R Quality Assurance Manual, Rev. 9, dated 4/1/2000.
 The following tests were performed on this order: TENSILE

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max →) 0.2% YS ksi (Min 72Max →) 4D Elong. % (Min 32Max →) Modulus Msi (Min 21Max →)
 SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: Metaltek CF8MNM00

| Coll No. | Specimen | TestLog Number | Temp. °F | UTS ksi | 0.2% YS ksi | Elong % | RA % | Modulus Msi | Ult. Load lbf | 0.2% YLD. lbf | Orig. Dia. (in.) | Final Dia. (in.) | 4D Orig. GL (in.) | 4D Final GL (in.) | Orig. Area (sq. in.) | Machine Number | Machine AUIR |
|----------|----------|----------------|----------|---------|-------------|---------|------|-------------|---------------|---------------|------------------|------------------|-------------------|-------------------|----------------------|----------------|--------------|
| A6 | Z2 | D30718 | -320 | 166.2 | 99.8 | 56 | 44 | 25.3 | 16120 | 5677 | 0.3514 | 0.2622 | 1.40 | 2.21 | 0.0968250 | h07 | A |

DISPOSITION: Acceptable

AU/R: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max →) 0.2% YS ksi (Min 72Max →) 4D Elong. % (Min 32Max →) Modulus Msi (Min 21Max →)
 SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: Metaltek CF8MNM00

| Coll No. | Specimen | TestLog Number | Temp. °F | UTS ksi | 0.2% YS ksi | Elong % | RA % | Modulus Msi | Codes | Ult Load lbf | 0.2% YLD. lbf | Orig. Dia. (in.) | Final Dia. (in.) | 4D Orig. GL (in.) | 4D Final GL (in.) | Orig. Area (sq. in.) | Machine Number | Machine AUIR |
|----------|----------|----------------|----------|---------|-------------|---------|------|-------------|-------|--------------|---------------|------------------|------------------|-------------------|-------------------|----------------------|----------------|--------------|
| A6 | Z1 | D30718 | -320 | 166.1 | 108.1 | 25 | 26 | 27.6 | - | 16050 | 10450 | 0.3508 | 0.3024 | 1.40 | 1.75 | 0.09685160 | M9 | U |
| A6 | Z3 | D30720 | -320 | 129.7 | 105.2 | 13 | 19 | 27.9 | D | 12540 | 10170 | 0.3508 | 0.3153 | 1.40 | 1.58 | 0.09685160 | M9 | U |

DISPOSITION: Unacceptable


AU/R: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

Requirements provided by MetalTek International
 D - Ruptured outside middle half of gage length.

KNOWLEDGE OF THESE RESULTS OR CONCERNING A MATERIAL FACT ON THIS FORM
 OR ANY OTHER FACT, INCLUDING BUT NOT LIMITED TO, THE RESULTS OF THESE TESTS,
 HEREIN, IS THE PROPERTY OF METALTEK INTERNATIONAL. IT IS TO BE KEPT
 CONFIDENTIAL AND NOT TO BE REPRODUCED OR TRANSMITTED IN ANY FORM OR BY ANY MEANS,
 ELECTRONIC OR MECHANICAL, INCLUDING PHOTOCOPYING, RECORDING, OR BY ANY INFORMATION
 STORAGE AND RETRIEVAL SYSTEM, WITHOUT THE WRITTEN APPROVAL OF METALTEK, INC.


M. J. ...
 E. Start...
 Technical Services Manager / Ferrous Supervisor
 4-3-06
 April 3, 2006

Testing Specialists for Aerospace, Automotive, and Material Testing Fields
 Locations in Youngstown, PA U.S.A. - Tel. (724) 537-3131 and
 Banbury U.K. - Tel. +44 (0) 1295 261211



Westmoreland Mechanical Testing & Research, Inc.

P.O. Box 388
 Westmoreland Drive
 Youngstown, Pa. 15696-0388 U.S.A.
 Telephone: 724-537-3131 Fax: 724-537-3151
 Website: www.wmtr.com
 WMTR is a technical leader in the material testing industry.



ACCREDITED
Nadcap
 Materials Testing Laboratory

621-01 & 621-02

Section 1 of 1

WMT&R Report No. 6-26780
 P.O. No. 19386
 Requisition No. 7560

CERTIFICATION

April 10, 2006

MetalTek International
 The Carondelet Division
 8600 Commercial Blvd.
 I-55 Industrial Park
 Pevely, MO 63070-1528

Attention: Jim Gelaaks

Subject: All processes, performed upon the material as received, were conducted at WMT&R, Inc. in accordance with the WMT&R Quality Assurance Manual, Rev. 9, dated 4/1/2000.
 The following tests were performed on this order: TENSILE

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max →) 0.2% YS ksi (Min 72Max →) 4D Elong. % (Min 32Max →) Modulus Msi (Min 21Max →)

SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: Metaltek CF8MMnMOD

| Coil No. | Specimen | TestLog Number | Temp. °F | UTS | | 0.2% YS | | Elong % | | RA % | | Modulus Msi | | Ult. Load lbf | | 0.2% YLD. lbf | | Orig. Dia. (in.) | | Final Dia. (in.) | | 4D Orig GL (in.) | | 4D Final GL (in.) | | Orig. Area (sq. in.) | | Machine Number | | DISPOSITION: Acceptable | |
|----------|----------|----------------|----------|-------|-----|---------|----|---------|------|-------|------|-------------|--------|---------------|------|---------------|-----|------------------|-----|------------------|-----|------------------|-----|-------------------|-----|----------------------|-----|----------------|-----|-------------------------|-----|
| | | | | ksi | ksi | ksi | % | % | % | Msi | Msi | lbf | lbf | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | | in. |
| A6 | Z2 | D38883 | -320 | 165.8 | 320 | 100.8 | 35 | 31 | 28.6 | 18070 | 9774 | 0.3513 | 0.2923 | 1.40 | 1.90 | 0.09692731 | M9 | A | | | | | | | | | | | | | |
| A6 | Z3 | D38884 | -320 | 160.9 | 320 | 93.7 | 44 | 41 | 25.5 | 15540 | 9049 | 0.3507 | 0.2686 | 1.40 | 2.02 | 0.09659650 | M9 | A | | | | | | | | | | | | | |

AIUR: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max →) 0.2% YS ksi (Min 72Max →) 4D Elong. % (Min 32Max →) Modulus Msi (Min 21Max →)

SOAK TIME: 5 Minutes

SPEED OF TESTING: 0.003 in./in./min., 0.05 in./min./in.

MATERIAL: Metaltek CF8MMnMOD

| Coil No. | Specimen | TestLog Number | Temp. °F | UTS | | 0.2% YS | | Elong % | | RA % | | Modulus Msi | | Ult. Load lbf | | 0.2% YLD. lbf | | Orig. Dia. (in.) | | Final Dia. (in.) | | 4D Orig GL (in.) | | 4D Final GL (in.) | | Orig. Area (sq. in.) | | Machine Number | | DISPOSITION: Unacceptable | |
|----------|----------|----------------|----------|-------|-----|---------|----|---------|------|-------|------|-------------|--------|---------------|------|---------------|-----|------------------|-----|------------------|-----|------------------|-----|-------------------|-----|----------------------|-----|----------------|-----|---------------------------|-----|
| | | | | ksi | ksi | ksi | % | % | % | Msi | Msi | lbf | lbf | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | in. | | in. |
| A6 | Z1 | D38882 | -320 | 134.7 | 320 | 100.2 | 20 | 23 | 26.0 | 13030 | 9700 | 0.3510 | 0.3084 | 1.40 | 1.68 | 0.09676184 | M9 | U | | | | | | | | | | | | | |

AIUR: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

Requirements provided by MetalTek International
 D - Ruptured outside middle half of gauge length.

Mattamy
 Roy E. Stamm
 Technical Services Manager
 April 10, 2006

KNOWLEDGE OF THIS DOCUMENT DOES NOT CONSTITUTE A WARRANTY OR ENDORSEMENT BY METALTEK INTERNATIONAL OF ANY PRODUCT OR SERVICE. METALTEK INTERNATIONAL IS NOT RESPONSIBLE FOR ANY DAMAGE TO PERSONS OR PROPERTY. THIS DOCUMENT IS THE PROPERTY OF METALTEK INTERNATIONAL AND IS NOT TO BE REPRODUCED WITHOUT THE WRITTEN PERMISSION OF METALTEK INTERNATIONAL.

Testing Specialists for Aerospace, Automotive, and Material Testing Fields
 Locations in Youngstown, PA U.S.A. - Tel. (724) 537-3131 and
 Banbury U.K. - Tel. +44 (0) 1295 261211

Addendum to CA 1671

Effect of Solidification Microstructure on Tensile Properties of Stellaloy

J. Edwards and C. Ruud, MetalTek International

Overview

The development of “Stellaloy” by MetalTek International commenced in 2003 with the modification of the base 316 material primarily for magnetic permeability requirements. Initial results demonstrated that this material is extremely robust mechanically at both ambient and cryogenic temperature ranges. Tensile properties gathered from integrally cast test specimens poured with the modules have shown variability. While most have far exceeded the specification minima, outliers have shown to demonstrate reduced elongation.

Background

Initial tests on the C5 casting showed that the elongation was lower in test bars associated with Zone1 than in other areas of the casting. Repeat tests showed the same result (Table I). Based on this result, the microstructure of the test specimen was examined and characterized compared to other test bars integral to the same modular coil casting. Results are shown in figures Lab report 05M1167, Figures 1, 2 and 3.

Similarly, testing of the A6 casting has shown a lower elongation in the test specimens associated with Zone 1. Testing was repeated in specimens from the same zone with reproducible results (25-26% elongation at 77K), although one test demonstrated a 20% elongation with breakage outside the gauge. Results of this test are shown in Table II and associated microstructures in Figures contained in WMTR#6-26780.

The tensile test variation seems to demonstrate correlation to microstructure with finer grains and heavily dendritic structures showing lower elongation. Other properties are generally well above specification for both samples.

The attached test specimens from the production coils are machined to a 0.350” diameter (“sub size” or SS) bar. The strain rate on the production components is 0.003 in/in/min to yield and 0.05 in/min/in to fracture.

Analysis

The test specimens are attached to metal feeders (“risers”) in the modular coil casting mold. The attachment of these test specimens is largely determined by convenience due to accessibility of the feeder and orientation to a natural interface between mold components (cope, drag, and cores). Metal is introduced into the mold through a series of ceramic tubes from any of 3 ladles and mixes naturally upon entry into the mold cavity. Attached test specimens are filled by the molten metal at different temperatures and at different elapsed time from mold filling onset. The combination of elapsed time and geometric location of the attached specimens results in a range of solidification structures based on the superheat of the metal entering the specimen as well as the rate of heat extraction from the metal through the sand wall due to mold temperature surrounding the specimen (Table III). In general, cooler metal temperatures favor multiple nucleation sites while cooler mold temperatures promote nucleation at an accelerated rate on the mold

surface. Hotter metal temperatures result in fewer nucleation sites and more growth of individual grains during solidification.

Results

1. The properties measured from attached test specimens vary; however, exceed the specification minima in most cases.
2. Isolated test bars have shown depressed elongation values of approximately 25-29%. Microstructural analysis of these test bars demonstrate that the microstructure is generally fine grained and may or may not contain heavily dendritic structure.
3. Test bar structure is the result of solidification physics of the test material and not associated with physical differences of Zone location.
4. Stellaloy continues to test well across a variety of microstructures at both 77K and RT.

| Table III | High Metal Temperature | Low Metal Temperature |
|-----------------------|---|--|
| High Mold Temperature | Little incentive for nucleation and low thermal gradients. Large columnar grains. | Multiple nucleation sites within material, but little thermal gradient to mold. Creates finely dispersed equiaxed structure within metal with little correlation to mold wall. |
| Low Mold Temperature | Strong dendritic structure with multiple mold surface nucleation sites. Relatively "fine" appearance of closely spaced dendrites. | Multiple nucleation sites with primary sites on mold walls. Intraspecimen nucleation as solidification progresses. Broken dendritic with equiaxed. |



Westmoreland Mechanical Testing & Research, Inc.
 P.O. Box 388
 Westmoreland Drive
 Youngstown, Pa. 15696-0388 U.S.A.
 Telephone: 724-537-3131 Fax: 724-537-3151
 Website: www.wmtr.com
WMTR is a technical leader in the material testing industry.

CERTIFICATION



Section 1 of 1
 WMTR Report No. 6-27410
 P.O. No. 18396
 Requisition No. 7580

April 19, 2006
 MetalTek International
 The Carondelet Division
 8600 Commercial Blvd.
 1-55 Industrial Park
 Pewee, MO 63070-1528

Attention: Jim Galaskie
 Subject: All processes, performed upon the material as received, were conducted at WMTR, Inc. in accordance with the WMTR Quality Assurance Manual, Rev. 9, dated 4/1/2000.
 The following tests were performed on this order: MICRO and TENSILE

TENSILE RESULTS: ASTM E21-05

Requirements: UTS ksi (Min 95Max →) 0.2% YS ksi (Min 72Max →) 4D Elong. % (Min 32Max →) Modulus Msi (Min 211Max →)
 SOAK TIME: 5 Minutes
 SPEED OF TESTING: 0.003 in./min., 0.05 in./min./in.

MATERIAL: Metaltek CFRMMNMCO

DISPOSITION: Acceptable

| Coil No. | Specimen Number | Temp. °F | UTS ksi | 0.2% YS ksi | Elong % | RA % | Modulus Msi | Ult. Load lbf | 0.2% YLD. lbf | Orig. Dia. (in.) | Final Dia. (in.) | 4D Orig. GL (in.) | 4D Final GL (in.) | Orig. Area (sq. in.) | Machine Number | AUVR |
|----------|-----------------|-------------|---------|-------------|---------|------|-------------|---------------|---------------|------------------|------------------|-------------------|-------------------|----------------------|----------------|------|
| A6 | Z1 | DA3805 -320 | 167.3 | 95.8 | 64 | 65 | 25.8 | 16150 | 9282 | 0.3506 | 0.2082 | 1.40 | 2.30 | 0.09654142 | M8 | A |
| A6 | Z2 | DA3806 -320 | 167.1 | 97.0 | 54 | 80 | 24.8 | 16180 | 9384 | 0.3511 | 0.1585 | 1.40 | 2.15 | 0.09681698 | M9 | A |
| A6 | Z3 | DA3807 -320 | 189.4 | 116.2 | 51 | 44 | 31.7 | 18300 | 11220 | 0.3507 | 0.2620 | 1.40 | 2.12 | 0.09659850 | M9 | A |

AUVR: A=ACCEPTABLE, U=UNACCEPTABLE, R=REPORT

Requirements provided by MetalTek International

APPROVED FOR RELEASE BY THE NATIONAL ARCHIVES AND RECORDS ADMINISTRATION
 ON APRIL 19, 2006
 METALTEK INTERNATIONAL
 8600 COMMERCIAL BLVD.
 PEWEE, MO 63070-1528

Testing Specialists for Aerospace, Automotive, and Material Testing Fields
 Locations in Youngstown, PA U.S.A. - Tel: (724) 537-3131 and
 Danbury, Vt. - Tel: +44 (0) 1295 261211

Matt Winters
 Roy E. Starnatt
 Technical Services Manager
 Tensile Supervisor
 April 19, 2006
 4-19-06